


# TECHNICAL FEATURES

TECNODECK® PLUS

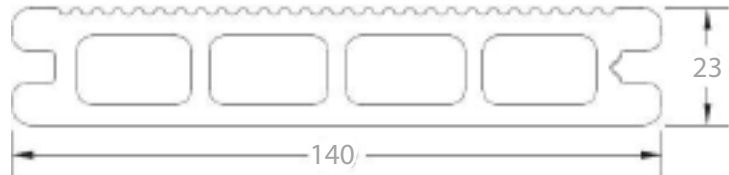

TECNODECK® PLUS

DENSITY EN ISO 1183-1 (g/cm<sup>3</sup>)

1,41

WEIGHT (Kg/ml)

2,65 (+/- 5%)

APPEARANCE

CLAUSE 6.1 of EN 15534-1:2014  
Legth of specimen: 1000mm

No visible colour difference

PENDULUM TEST

CLAUSE 6.4.2 of EN 15534-1:2014 and  
CEN/TS 15676:2007  
Requirements of EN 15534-4:2014  
Pendulum value  $\geq 36$

Pendulum value of face surface:

Length direction: 62  
Width direction: 72

FALLING MASS IMPACT RESISTANCE

CLAUSE 7.1.2.1 of EN 15534-1:2014 and  
CEN/TS 15676:2007  
Requirements of EN 15534-4:2014  
Hollow profiles:  
None of 10 test specimens shall show a failure with a crack length  $\geq 10$ mm or a depth of residual indentation  $\geq 0,5$ mm. In case of failure, 10 additional test specimens shall be tested and no failure with a crack length  $\geq 10$ mm or a depth of residual indentantion  $\geq 0,5$ mm shall occur.

None of 10 test specimens showed a crack on face surface.  
Maximum depth of residual indentation: 0.13mm

SLIP RESISTANCE DIN 51130:2014, SLIP ANGLE 33,9°

R11

v.01/2022

---

**FLEXURAL PROPERTIES**

CLAUSE 7.3.2 of EN 15534-1:2014  
Requirements of EN 15534-4:2014  
F<sub>max</sub> ≥ 3300 N  
(arithmetic mean value)  
F<sub>max</sub> ≥ 3000 N  
(individual values)  
Deflection under a load of 500 N ≤  
2,0mm (arithmetic mean value)  
Deflection under a load of 500 N ≤  
2,5mm (individual values)  
Span: 300mm

Average F<sub>max</sub>: 4177N  
Minimum F<sub>max</sub>: 4013N  
Average deflection under 500N: 0.52mm  
Maximum deflection under 500N: 0.62mm  
Average bending strength: 28.9MPa  
Average modulus of elasticity: 4120MPa

---

**RESISTANCE TO INDENTATION**

CLAUSE 7.5 of EN 15534-1:2014  
Requirements of EN 15534-4:2014  
Load rate: 66 N/S  
Final Load: 2000N

Brinell hardness: 54N/mm<sup>2</sup>  
Rate of elastic recovery: 75%

---

**CREEP BEHAVIOR (KNOWN SPAN IN USE)**

CLAUSE 7.4.1 of EN 15534-1:2014  
Requirements of EN 15534-4:2014  
Testing atmosphere: 24±2 °C, 50±5% RH  
Span: 300mm (Manufacture declare)  
Load: 1000 N  
Loading duration: 504h  
Recovering duration: 24h  
Requirements of  
EN 15534-4:2014:  
Δ S ≤ 10mm for arithmetic mean value  
Δ S ≤ 13mm for individual values  
Δ S<sub>r</sub> ≤ 5mm for arithmetic mean values

ΔS (arithmetic mean value): 1.24mm  
ΔS (Maximum individual value): 1.37mm  
ΔS<sub>r</sub> (arithmetic mean value): 0.86mm

---

**RESISTANCE TO ARTIFICIAL WEATHERING**

CLAUSE 8.1 of EN 15534-1:2014 ,  
Cycle 1 of EN ISO 4892-2:2013  
Duration: 2000h  
Requirements of EN 15534-4:2014:  
ΔL\*, Δa\*, Δb\* shall be declared.

ΔE\*: 0.99  
Grey scale: 4-5  
(No declared value)

---

**TENSILE STRENGTH PERPENDICULAR TO THE  
PANEL AFTER ARTIFICIAL WEATHERING**

EN 319:1993 and Cycle 1 of EN ISO 4892-2:2013  
and client's requirements  
Duration: 2000h  
Test speed: 0.5mm/min

Average value: 1.63MPa  
Failure mode: Adhesive failure  
(See note)

---

**MOISTURE RESISTANCE - BOILING TEST**

Clause 8.3.3 of EN 15534-1:2014, EN 319:1993  
and client's requirements  
Requirements of EN 15534-4:2014  
Mean water absorption ≤ 7%  
Individual water absorption ≤ 9%

Water absorption:  
Average value: 0.67%  
Maximum value: 1.03%  
Length change: 0.22%  
Width change: 0.16%  
Thickness change: 1.60%

---

**FIRE BEHAVIOUR**

Not tested

---

**TENSILE STRENGTH PERPENDICULAR TO THE PANEL AFTER BOILING TEST**

EN 319:1993, clause 8.3.3 of  
EN 15534-1:2014  
and client's requirements  
Test speed: 0.5mm/min

Average value: 1.54MPa  
Failure mode: Adhesive failure  
(See note)

---

**MOISTURE RESISTANCE****- UNDER CYCLIC CONDITIONS**

Clause 8.3.2 of EN 15534-1:2014  
Requirements of EN 15534-4:2014  
Mean of decrease of bending strength  
 $\leq 20\%$   
Individual decrease of bending  
strength  $\leq 30\%$

Average bending strength:  
25.6MPa  
Average modulus of elasticity: 3293MPa  
Mean of decrease of bending strength: 11.4%  
Maximum individual decrease of bending: 15.3%

Average value:  
Water absorption: 0.19%  
Length change: 0.01%  
Width change: 0.11%  
Thickness change: 0.22%

---

**TENSILE STRENGTH PERPENDICULAR TO THE PANEL UNDER CYCLIC CONDITIONS**

EN 319:1993, clause 8.3.2 of EN 15534-  
1:2014 and client's requirements  
Test speed: 0.5mm/min

Average value: 0.69MPa  
Failure mode: Core material

---

**\*LINEAR THERMAL EXPANSION**

Clause 9.2 of EN 15534-1:2014  
Temperature range: -20°C to 80°C  
Requirements of EN  
15534-4:2014:  
Linear thermal expansion  
coefficient  $\leq 50 \times 10^{-6} \text{ K}^{-1}$

Average value of the coefficient  
of linear thermal expansion:  $36 \times 10^{-6} \text{ K}^{-1}$   
(length direction)

---

**HEAT REVERSION**

Clause 9.3 of EN 15534-1:2014  
Specimen: 250x137x22mm  
Heating: 100°C, 60min

Average length change: 0.20%

---

**\*RESISTANCE AGAINST DISCOLOURING MICRO-FUNGI**

Clause 9.3 of EN 15534-1:2014  
Specimen: 250x137x22mm  
Heating: 100°C, 60min

Rate: 0  
No covering or  
discoloration visible

---

**DEGREE OF CHALKING (APPLICABLE TO COATED PRODUCTS, ONLY)**

Clause 10.1 of EN 15534-1:2014 and  
ISO 16869:2008(E)

The product is uncoated

---

**TENSILE STRENGTH PERPENDICULAR TO THE PANEL**

Clause 10.1 of EN 15534-1:2014 EN 319:1993  
Test speed: 0.5mm/min

Average value: 1.59MPa  
Failure mode: Adhesive failure  
(See note)

---

**ABRAISON RESISTANCE**

ASTM D4060-14  
Wheel; CS-17  
Load: 1Kg/wheel  
Revolution: 1000r

Wear Index: 31mg/1000r

---

v.01/2022

**NOTE:**

The Tecnodeck® profiles dimensions have a tolerance of  $\pm 1\text{mm}$ .  
These features are only for information purposes, and the manufacturer  
may change them without previous notice.